

**Yb:KGW AND Yb:KYW CRYSTALS LASER LINES AND HARMONICS**



Yb:KGW and Yb:KYW crystals have broad emission bandwidths and are used as lasing materials to generate ultrashort (~100-200 fs) high power pulses. Direct pump of Yb:KGW/KYW crystals with laser diodes operating at 981 nm supports compact laser systems. Yb:KGW/KYW laser generates pulses at 1023-1060 nm wavelength range.

Also Yb:KGW and Yb:KYW can be used as ultrashort pulse amplifiers.

We believe that Yb:KGW and Yb:KYW are some of the best materials for high power thin disk lasers generating femtosecond pulses.


**CUSTOM MANUFACTURING CAPABILITIES**

- Various shapes (slabs, rods, cubes, disks)
- Different dopant levels
- Diversified coatings
- Attractive prices for introductory quantities to OEMs


- High absorption coefficient at 981 nm
- High stimulated emission cross section
- Low laser threshold
- Extremely low quantum defect  $\lambda_{pump} / \lambda_{se}$
- Broad polarized output at 1023–1060 nm
- High slope efficiency with diode pumping (~ 60%)
- High Yb doping concentration

**PROPERTIES OF Yb:KGW AND Yb:KYW**

Name	Yb:KGW	Yb:KYW
Yb <sup>3+</sup> concentration	0.5–5%	0.5–100%
Crystal structure	monoclinic	monoclinic
Point group	C2/c	C2/c
Lattice parameters	a=8.095 Å, b=10.43 Å, c=7.588 Å, β=94.43°	a=8.05 Å, b=10.35 Å, c=7.54 Å, β=94°
Thermal expansion	$\alpha_a=4 \times 10^{-6} / ^\circ\text{C}$ , $\alpha_b=3.6 \times 10^{-6} / ^\circ\text{C}$ , $\alpha_c=8.5 \times 10^{-6} / ^\circ\text{C}$	—
Thermal conductivity	$K_a=2.6 \text{ W/mK}$ , $K_b=3.8 \text{ W/mK}$ , $K_c=3.4 \text{ W/mK}$	—
Density	7.27 g/cm <sup>3</sup>	6.61 g/cm <sup>3</sup>
Mohs' hardness	4–5	4–5
Melting temperature	1075 °C	—
Transmission range	0.35–5.5 μm	0.35–5.5 μm
Refractive indices (λ=1.06 μm)	$n_y=2.037$ , $n_p=1.986$ , $n_m=2.033$	—
$\partial n / \partial t$	$0.4 \times 10^{-6} \text{ K}^{-1}$	$0.4 \times 10^{-6} \text{ K}^{-1}$
Laser wavelength	1023–1060 nm	1025–1058 nm
Fluorescence lifetime	0.3 ms	0.3 ms
Stimulated emission cross section (E    a)	$2.6 \times 10^{-20} \text{ cm}^2$	$3 \times 10^{-20} \text{ cm}^2$
Absorption peak and bandwidth	$\alpha_a=26 \text{ cm}^{-1}$ , λ=981 nm, Δλ=3.7 nm	$\alpha_a=40 \text{ cm}^{-1}$ , λ=981 nm, Δλ=3.5 nm
Absorption cross section	$1.2 \times 10^{-19} \text{ cm}^2$	$1.33 \times 10^{-19} \text{ cm}^2$
Lasing threshold	35 mW	70 mW
Stark levels energy (in cm <sup>-1</sup> ) of the <sup>2</sup> F <sub>5/2</sub> manifolds of Yb <sup>3+</sup> @ 77K	10682, 10471, 10188	10695, 10476, 10187
Stark levels energy (in cm <sup>-1</sup> ) of the <sup>2</sup> F <sub>7/2</sub> manifolds of Yb <sup>3+</sup> @ 77K	535, 385, 163, 0	568, 407, 169, 0

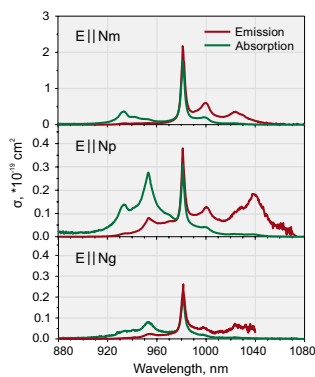

Absorption and stimulated emission cross sections of Yb:KYW

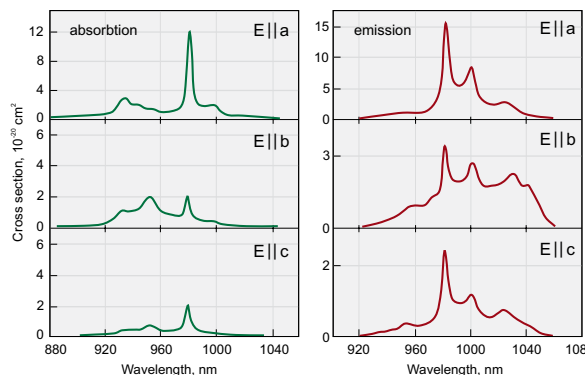

Absorption and emission spectrae of Yb(5%):KGW